

## PRODUCT DATA SHEET

# Indium5.8LS-4.5

## Pb-Free Solder Paste

### Introduction

**Indium5.8LS-4.5** is an air reflow, no-clean solder paste specifically formulated to accommodate the higher processing temperatures required by the SnAgCu, SnAg, and other alloy systems favored by the electronics industry to replace conventional Pb-bearing solders. **Indium5.8LS-4.5** offers unprecedented stencil print transfer efficiency to work in the broadest range of processes. In addition, the high probe testability of **Indium5.8LS-4.5** minimizes false failures in ICT.

### Features

- Halogen-free per EN14582 test method
- High transfer efficiency through small apertures ( $\leq 0.66AR$ )
- Eliminates hot and cold slump
- High oxidation resistance
- Wets well to oxidized BGA and pad surfaces
- Excellent soldering performance under high temperature and long reflow processes
- Clear, probe testable flux residue
- Backward compatible with SnPb alloys

### Alloys

Indium Corporation manufactures low-oxide spherical powder composed of a variety of Pb-free alloys that cover a broad range of melting temperatures. The metal percent is the weight percent of the solder powder in the solder paste and is dependent upon the powder type and application. Standard product offerings are detailed in the following table.

### Standard Product Specifications

Alloy	Metal Load
SAC305	88.25% (Type 4.5)

### Belcore and J-STD Tests and Results

Test	Result	Test	Result
J-STD-004 (IPC-TM-650)		J-STD-005 (IPC-TM-650)	
Flux Type (per J-STD-004A)	ROLO	Typical Solder Paste Viscosity Malcom (10rpm) (88.25% Type 4.5)	1,700 poise
Flux Induced Corrosion (Copper Mirror)	Type L	Slump Test	Pass
Presence of Halide Oxygen Bomb Followed by Ion Chromatography	<100ppm	Solder Ball Test	Pass
SIR	Pass)	Typical Tackiness	35 grams
All information is for reference only. Not to be used as incoming product specifications.		Wetting Test	Pass
		BELLCORE GR-78	
		SIR	Pass
		Electromigration	Pass

### Storage and Handling Procedures

Refrigerated storage will prolong the shelf life of solder paste. The shelf life of **Indium5.8LS-4.5** is 6 months when stored at  $<10^{\circ}\text{C}$ . Solder paste packaged in cartridges should be stored tip down.

Solder paste should be allowed to reach ambient working temperature prior to use. Generally, paste should be removed from refrigeration at least 2 hours before use. Actual time to reach thermal equilibrium will vary with container size. Paste temperature should be verified before use. Jars and cartridges should be labeled with date and time of opening.

### Packaging

**Indium5.8LS-4.5** is currently available in 500g jars or 600g cartridges. Packaging for enclosed print head systems is also readily available. Alternate packaging options may be available upon request

### Complementary Products

- **Rework Flux:** TACFlux<sup>®</sup> 020B, TACFlux<sup>®</sup> 089HF
- **Cored Wire:** CW-802
- **Wave Flux:** WF-7742, WF-9945

*Note: Other products may be applicable. Please consult one of Indium Corporation's Technical Support Engineers.*

From One Engineer To Another<sup>®</sup>



## PRODUCT DATA SHEET

# Indium5.8LS-4.5 Pb-Free Solder Paste

## Printing

### Stencil Design:

Electroformed and laser cut/electropolished stencils produce the best printing characteristics among stencil types. Stencil aperture design is a crucial step in optimizing the print process. The following are a few general recommendations:

- Discrete components—A 10–20% reduction of stencil aperture has significantly reduced or eliminated the occurrence of mid-chip solder beads. The “home plate” design is a common method for achieving this reduction.
- Fine pitch components—A surface area reduction is recommended for apertures of 20mil pitch and finer. This reduction will help minimize solder balling and bridging that can lead to electrical shorts. The amount of reduction necessary is process-dependent (5–15% is common).
- For optimum transfer efficiency and release of the solder paste from the stencil apertures, industry standard aperture and aspect ratios should be adhered to.

## Recommended Printer Operation

Solder Paste Bead Size	~20–25mm in diameter
Print Speed	25–100mm/second
Squeegee Pressure	0.018–0.027kg/mm of blade length
Underside Stencil Wipe	Start at once per every 5 prints and decrease frequency until optimum value is reached
Solder Paste Stencil Life	>8 hours (at 30–60% RH and 22–28°C)


## Cleaning

**Indium5.8LS-4.5** is designed for no-clean applications; however the flux can be removed, if necessary, by using a commercially available flux residue remover.

**Stencil cleaning** is best performed using isopropyl alcohol (IPA) as a solvent. Most commercially available stencil cleaners work well.

## Reflow

### Recommended Profile:

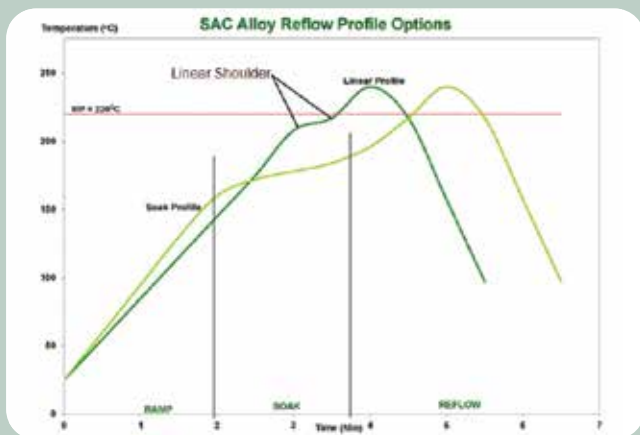

The stated profile recommendations apply to most Pb-free alloys in the SnAgCu (SAC) alloy system, including SAC305 (96.5Sn/3.0Ag/0.5Cu). This can be used as a general guideline in establishing a reflow profile when using **Indium5.8LS-4.5** solder paste. Deviations from these recommendations are acceptable, and may be necessary, based on specific process requirements, including board size, thickness, and density.

Reflow Profile Details	SAC305 Parameters		Comments
	Recommended	Acceptable	
Ramp Profile (Average Ambient to Peak)—Not the Same as Maximum Rising Slope	1.0–1.5°C/second	0.5–2.5°C/second	To minimize solder balling, beading, hot slump
Soak Zone Profile (Optional)	20–60 seconds	30–120 seconds	May minimize BGA/CSP voiding Eliminating/reducing the soak zone may help to reduce HIP and graping
	140–160°C	140–170°C	
Time Above Liquidus (TAL)	45–60 seconds	30–100 seconds	Needed for good wetting/reliable solder joint
Peak Temperature	230–260°C	230–262°C	As measured with thermocouple
Cooling Ramp Rate	2–6°C/second	0.5–6.0°C/second	Rapid cooling promotes fine-grain structure
Reflow Atmosphere	Air or N <sub>2</sub>		N <sub>2</sub> preferred for small components

All parameters are for reference only.

Modifications may be required to fit process and design.

This product data sheet is provided for general information only. It is not intended, and shall not be construed, to warrant or guarantee the performance of the products described which are sold subject exclusively to written warranties and limitations thereon included in product packaging and invoices. All Indium Corporation's products and solutions are designed to be commercially available unless specifically stated otherwise.

All of Indium Corporation's solder paste and preform manufacturing facilities are IATF 16949:2016 certified. Indium Corporation is an ISO 9001:2015 registered company.

Contact our engineers: [askus@indium.com](mailto:askus@indium.com)

Learn more: [www.indium.com](http://www.indium.com)

ASIA +65 6268 8678 • CHINA +86 (0) 512 628 34900 • EUROPE +44 (0) 1908 580400 • USA +1 315 853 4900



©2022 Indium Corporation